

Spherical porous granules in MgOFe₂O₃Nb₂O₅ system: In situ observation of formation behavior using high-temperature confocal laser-scanning microscopy

著者別名	鈴木 義和
journal or publication title	Journal of the European Ceramic Society
volume	37
number	16
page range	5339-5345
year	2017-12
権利	(C) 2017. This manuscript version is made available under the CC-BY-NC-ND 4.0 license http://creativecommons.org/licenses/by-nc-nd/4.0/
URL	http://hdl.handle.net/2241/00149231

doi: 10.1016/j.jeurceramsoc.2017.05.056

1
2
3 **Spherical porous granules in MgO–Fe₂O₃–Nb₂O₅ system: *In situ* observation of formation**
4 **behavior using high-temperature confocal laser-scanning microscopy**
5
6

7 Yoshikazu Suzuki,^{a*} Hiroya Abe^b, Hajime Yamamoto^b, Kazuhiro Ito^b, Hiroshige Inoue^b, Mayumi
8 Nakamura^c

9 ^a Faculty of Pure and Applied Sciences, University of Tsukuba, 1-1-1 Tennodai, Tsukuba, Ibaraki,
10 305-8573, Japan

11 ^b Joining and Welding Research Institute, Osaka University, 11-1 Mihogaoka, Ibaragi, Osaka
12 567-0047, Japan

13 ^c Yonekura MFG Co., 2-11-5, Shin-Yokohama, Kohoku, Yokohama, Kanagawa, 222-0033, Japan
14
15
16

17 **Abstract**

18 The pyrolytic reactive granulation process, yielding ceramic spherical porous granules, is simple,
19 consisting of typical ceramic processing methods, *viz.*, wet-ball milling of powders, vacuum drying,
20 granulation via sieving through a screen mesh, and one-step heat treatment for local reactive
21 sintering within each granule. Here, the microstructural development of spherical porous granules
22 was successfully visualized by *in situ* high-temperature confocal laser-scanning microscopy during
23 the heating up to 1400°C in air. Based on the result of the *in situ* observation, a simple but powerful
24 size-controlling process of spherical porous granules, *viz.*, multiscreen sieving after the heating was
25 demonstrated. Nearly monodispersed spherical porous granules composed of pseudobrookite-type
26 MgFeNbO₅ were easily obtained.
27
28
29
30
31
32

33
34 **Keywords:** spherical porous granule (SPG), *in situ* observation, confocal laser-scanning microscopy
35 (CLSM), pseudobrookite, MgFeNbO₅
36
37
38
39
40

41 **1. Introduction**

42 Spherical porous granules (SPGs) are promising for many applications, *e.g.*, heterogeneous
43 catalysts, catalyst supports, drug delivery carriers, healing of defective bones and so on [1-8]. A
44 variety of processes have been developed to form SPGs; they are mostly liquid-based processes,
45 particularly spray drying [1,2], suspension hardening [3,4], drop-in-oil [5], sol-gel granulation [6]
46 and freeze-granulation [2,7]. Solid-based processes are rarely realized for the SPG production,
47 except the mechanical granulation method with a rotating fluidized bed [8]. Recently, we have
48 reported a new solid-based process to synthesize SPGs by a one-step heat-treatment of the
49 MgCO₃(basic)- α -Fe₂O₃-Nb₂O₅ mixed powder. Pseudobrookite-type MgFeNbO₅ SPGs with 3-D
50
51
52
53
54
55

56
57

* Corresponding Author

58 E-mail: suzuki@ims.tsukuba.ac.jp

59 Tel: +81-29-853-5026 / Fax: +81-29-853-4490
60
61
62
63
64
65

1
2
3 network structure, typically 50-100 μm in diameter, were successfully obtained (Fig. 1) [9].

4 This pyrolytic reactive granulation (PRG) process is really simple, consisting only of typical
5 ceramic processes, *viz.*, wet-ball milling of starting powders, vacuum drying, granulation via sieving
6 through a screen mesh, and a simple heat treatment (without pressing). Nevertheless, this new
7 mechanical and solid-based process yields porous granules with relatively high sphericity [9]. This
8 PRG process is similar to the pyrolytic reactive sintering process used to obtain bulk porous
9 ceramics [10-12]; emitted CO_2 or H_2O gas in starting carbonates, hydroxides etc. formed a uniformly
10 open porous 3-D network structure with pore diameter of $\sim 1 \mu\text{m}$. The final diameter (typically
11 50-100 μm) of SPGs by the pyrolytic reactive granulation is probably governed by the opening size
12 of sieving mesh ($< 150 \mu\text{m}$) used in the powder process before the heating.
13
14
15
16
17

18 Previously [9], microstructure development during heating was investigated with *ex situ* (i.e.,
19 ordinary) SEM observation for the samples after heating at intermediate temperatures. With an *ex*
20 *situ* SEM observation, dynamic microstructure development cannot be followed. *In situ*
21 high-temperature (HT) microscopy is effective to dynamically pursue the microstructure
22 development during the heating. Depending on the sample size/shape and the required resolution,
23 optical microscopy (OM), scanning electron microscopy (SEM) [13-15], transmission electron
24 microscopy (TEM) [16-18] and scanning probe microscopy (SPM) [19] have been combined with
25 HT observation. Recently, confocal laser-scanning microscopy (CLSM), an advanced type of optical
26 microscopy, can be utilized for the HT observation, where an infrared image furnace enables the HT
27 observation up to as high as 1800°C in air. The HT-CLSM is increasingly being used in metallurgy
28 and ceramic fields [20-23].
29
30
31
32
33
34
35

36 Here the primary purpose is to clarify the microstructural development during the heating of
37 SPGs by using the HT-CLSM. The secondary purpose, based on the outcome from the HT-CLSM, is
38 to develop a facile size-control method for SPGs.
39
40
41

42 **2. Experimental**

43 *2.1. Materials*

44 As before [9], commercially available MgCO_3 (basic) (hydromagnesite,
45 $\text{Mg}_5(\text{CO}_3)_4(\text{OH})_2 \cdot 4\text{H}_2\text{O}$, 99.9%, Kojundo Chemical Laboratory), $\alpha\text{-Fe}_2\text{O}_3$ and Nb_2O_5 (99.9% each,
46 Wako Pure Chemical Ind.) powders were used as the starting materials. Prior to the weighing,
47 TG-DTA analysis (up to 1000°C) on the MgCO_3 (basic) powder was conducted to determine the
48 weight-loss during the heating. The MgCO_3 (basic), $\alpha\text{-Fe}_2\text{O}_3$ and Nb_2O_5 powders (Mg:Fe:Nb = 1:1:1
49 in mole fraction) were wet-ball milled for 24 h in ethanol with ZrO_2 balls, vacuum dried and sieved
50 through 100 mesh screen ($< 150 \mu\text{m}$).
51
52
53
54
55
56
57

58 *2.2. In situ high-temperature observation*

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

A confocal laser scanning microscope using a 408 nm violet laser (VL2000DX, Lasertec, Japan) equipped with a high-temperature *in-situ* observation system is used with an infrared image furnace (SVF17SP, Yonekura, Japan, as shown in Fig. S1). The $\text{Mg}_5(\text{CO}_3)_4(\text{OH})_2 \cdot 4\text{H}_2\text{O} - \text{Fe}_2\text{O}_3 - \text{Nb}_2\text{O}_5$ mixed powder in a small alumina crucible (6.5 mm ϕ) was observed up to 1400°C under flowing air with a ramp rate of 100°C/min for R.T.-800°C and 20°C/min for 800-1400°C.

2.3. Synthesis and size control of spherical porous granules

The $\text{Mg}_5(\text{CO}_3)_4(\text{OH})_2 \cdot 4\text{H}_2\text{O} - \text{Fe}_2\text{O}_3 - \text{Nb}_2\text{O}_5$ mixed powder in an alumina crucible was heated to 1300°C in a box furnace (ramp rate: 5°C/min) with 30 min holding at the maximum temperature. The temperature of the furnace was verified using TempCHEK pellets (Orton, USA). The constituent phases of SPGs were analyzed by X-ray diffraction (XRD, Cu-K α , 40 kV and 40 mA, Multiflex, Rigaku, Japan). Quantitative composition analysis of the Pt-coated SPGs was carried out with SEM-EDS (SU-70, Hitachi / INCA System, Oxford) at the acceleration voltage of 15 kV. Based on the preliminary result of HT-CLSM observation, we decided to use multiple screens for the classification of spherical porous granules (Fig. 2); it is an old-fashioned way, but is really cost effective and compatible with industrial powder processes. Using 3 meshes with different openings (150, 100 and 75 μm), SPGs were classified with manual vibration for ~5 min. The classified SPGs were observed by SEM, and their diameter values (500 granules for each sample) were determined by image analysis using Image-J software.

3. Results

3.1. *In situ* high-temperature observation

Figure 3 shows the microstructure development of SPGs observed by HT-CLSM. Percentages in photos show the diameter change of a selected granule during the heating. Shrinkage of the granules is clearly observed from 120 to 900°C, which is mainly attributed to the pyrolysis of $\text{Mg}_5(\text{CO}_3)_4(\text{OH})_2 \cdot 4\text{H}_2\text{O}$. At around 1100-1300°C, the sphericity improves caused by the reactions and rearrangements of the constituent grains, in particular for larger granules. The MgFeNbO_5 porous granules retained their spherical shape up to ~1350°C (with gradual densification), but began to be consolidated at ~1400°C due to local eutectic liquid phase formation. The *in situ* high-temperature observation clearly demonstrates the size change during the pyrolytic reactive granulation, which suggests that the classification (unification of the size) of rigid MgFeNbO_5 SPGs should be much easier after heating than that of soft agglomerates before heating.

3.2. Synthesis and size control of SPGs

Figure 4 shows an XRD pattern of SPGs, showing almost single-phase pseudobrookite-type MgFeNbO_5 with a trace of spinel phase, as seen in the previous work [9]. Some isolated intermediate,

1
2 but rather stable, spinel grains co-existed in the porous structure. Figure 5 shows a result of
3 SEM-EDS wide-area analysis of an MgFeNbO₅ SPG. Semi-quantitative analysis using INCA
4 software indicated that the SPG was composed of 11.6 at.% Mg, 11.9 at.% Fe, 12.1 at.% Nb and
5 64.5 at.% O, which are close to the ideal composition of 12.5 at.% of each metal and 62.5 at.% of
6 oxygen. Note that the estimated error by Pt coating is less than 1 at.% in this study. The uniformly
7 open-porous structure is composed of somewhat elongated grains with irregular shapes as commonly
8 observed for pseudobrookite-type ceramics.
9

10
11 Figure 6 shows SEM micrographs and particle-size distributions for SPGs after multiscreen
12 classification/sampling: (a) between 100 and 150 μm openings (sample A), and (b) between 75 and
13 100 μm openings (sample B). Due to the mild manual vibration/sieving, some finer granules still
14 remained for both samples in Fig. 6. However, nearly monodispersed granules can be easily obtained
15 by such an "old-fashioned" but versatile method. Note that some granules with ellipsoid-like or
16 irregular morphologies passed through the mesh possessed somewhat larger sphere-equivalent
17 diameters. It is also noteworthy that, as is seen in HT-CLSM, larger granules tend to have better
18 sphericity, which is confirmed by the aspect ratio analysis.
19

20 The BET surface area of samples A and B were 0.52 m²/g and 0.57 m²/g, respectively. These
21 values are similar to those of bulk UPC-3D (uniformly porous ceramics with 3-D network structure)
22 as before [10,11].
23
24
25

26 27 28 29 30 31 32 33 **4. Discussion**

34 *4.1. Microstructure development of SPGs*

35 For the *ex situ* SEM observation [9], sample preparation steps (*e.g.* fixation of granules on
36 carbon tape using a spatula) somewhat affected the macroscopic sample shapes, particularly for the
37 soft granules. After the pyrolysis of Mg₅(CO₃)₄(OH)₂•4H₂O phase (*i.e.*, MgO nanoparticle
38 formation) at intermediate temperatures, the mechanical strength of the granules seems be weak, and
39 hence, the macroscopic sample shapes can be easily collapsed. A major advantage of the *in situ*
40 method, as here, is that it avoids a deformation of the shapes of granules during the preparation
41 necessary in the *ex-situ* method [9]. Another advantage is to avoid the secondly atmosphere effect of
42 H₂O and CO₂ in air reacting with *e.g.* MgO nanoparticles,
43
44
45
46
47

48 The diameter of a selected granule (Fig. 3) decreased by 50-60% of the initial size. This
49 shrinkage for SPG was more extensive than that for bulk green samples with pre-pressing. Without
50 macroscopic liquid phase formation, each granule can unrestrictedly deform. Based on the *in situ*
51 HT-XRD [9] and the HT-CLSM analyses in this study, the microstructure development of SPGs
52 during the heating is schematically illustrated in Fig. 7. Even before the heating, the mixed powder
53 was composed of "spherical-like" granules with somewhat large size distribution. During the heating,
54 pyrolysis of Mg₅(CO₃)₄(OH)₂•4H₂O occurred, and thus, the granules were shrunk. Formation of
55
56
57
58
59
60
61
62
63
64
65

1
2 intermediate binary oxides (MgNb_2O_6 (ss), MgFe_2O_4 (ss) and FeNbO_4 (ss)) and ternary oxide
3 (MgFeNbO_5) helped to rearrange the grain networks, and thereby improved the macroscopic
4 sphericity. Up to 1350°C , without macroscopic liquid phase formation, the porous granules retained
5 their spherical shapes.
6
7
8
9

10 4.2. Size control of SPGs

11 As is stated in Section 3.1, the classification (unification of the size) of rigid MgFeNbO_5 SPGs
12 with 3-D network structure after the heating should be much easier than that of soft agglomerates of
13 the mixed powder before the heating. It is demonstrated (Fig. 6) that some SPGs by furnace heating
14 (not by the *in situ* observation) had the diameter of $\sim 150\ \mu\text{m}$, which implies the size shrinkage under
15 the slower heating rate became milder. Formation of the 3-D network structure may result in such
16 mild shrinkage (or even expansion) during the heating [24].
17
18
19
20
21
22

23 4.3. Potential applications of SPGs

24 Although the base compound, MgTi_2O_5 , does not show high catalytic activity (except
25 photocatalytic activity), these ternary compounds, MgFeNbO_5 and MgFeTaO_5 (as originally reported
26 by Bayer [25]) may be useful as redox catalysts. The specific surface area of the SPGs is relatively
27 small, but the spherical granular shape with open pores should be favorable for heterogeneous
28 catalysis. Moreover, MgFeNbO_5 SPGs might be applied for biomaterials because MgFeNbO_5 is
29 composed only of biocompatible elements.
30
31
32
33
34
35

36 5. Conclusions

37 We have attempted in this study (1) to clarify the microstructural development during the
38 heating of SPGs by using the HT-CLSM, and (2) to develop a facile size-control method of SPGs.
39 Thus,
40

41
42 (1) The size and morphological change of SPGs during heating was successfully observed by *in situ*
43 HT-CLSM. At around $1100\text{--}1300^\circ\text{C}$, the sphericity seems to be quite improved caused by the
44 reactions and rearrangements of the constituent grains, in particular for larger granules.
45

46
47 (2) The classification via multiscreen sieving for the rigid MgFeNbO_5 SPGs after heating was
48 effective for the size-unification. This very simple, old-fashioned technique enabled nearly
49 monodispersed SPGs.
50
51
52

53 Acknowledgements

54 This work was supported by JSPS KAKENHI Grant Number JP16H04212 for Basic Research:
55 Category B, and Joint Research Project of JWRI, Osaka University. We thank to Dr. Peter E. D.
56 Morgan to improve the language.
57
58
59
60
61
62
63
64
65

References

- [1] H. W. Chang, K. Okuyama, Optical properties of dense and porous spheroids consisting of primary silica nanoparticles, *J. Aerosol Sci.* 33 (2002) 1701-1720.
- [2] E. Garcia, J. Mesquita-Guimarães, P. Miranzo, M.I. Osendi, Porous mullite and mullite-ZrO₂ granules for thermal spraying applications, *Surf. Coat. Tech.* 205 (2011) 4304-4311.
- [3] W. Paul, C.P. Sharma, Development of porous spherical hydroxyapatite granules: application towards protein delivery, *J. Mater. Sci. Mater. Med.* 10 (1999) 383-388.
- [4] V.S. Komlev, S.M. Barinov, E.V. Koplík, A method to fabricate porous spherical hydroxyapatite granules intended for time-controlled drug release, *Biomaterials* 23 (2002) 3449-3454.
- [5] S.G. Deng, Y.S. Lin, Granulation of sol-gel-derived nanostructured alumina *AIChE J.* 43 (1997) 505-514.
- [6] Y.K. Nakamura, T.N. Murakami, N.Y. Iwata, Y. Hirano, Y. Tokuoka, N. Kawashima, Preparation of porous diopside microspheres from spherical silica gels impregnated with Ca(NO₃)₂ and MgCl₂, *J. Ceram. Soc. Jpn.* 112 (2004)133-137.
- [7] F. Paul, J.R. Binder, H. Gesswein, H.J. Ritzhaupt-Kleissl, J.Hausselt, Synthesis of doped Ba_{0.6}Sr_{0.4}TiO₃ ceramic powder via a sol-freeze-granulation and freeze-drying process, *Ceram. Int.* 35 (2008) 479-486.
- [8] S. Watano, Y. Imada, K. Hamada, Y. Wakamatsu, Y. Tanabe, R.N. Dave, R. Pfeffer, Microgranulation of fine powders by a novel rotating fluidized bed granulator, *Powder Technol.* 131 (2003) 250-255.
- [9] Y. Suzuki, H. Tokoro, H. Abe, Self-organized formation of spherical porous granules only by one-step heat-treatment in MgO-Fe₂O₃-Nb₂O₅ system, *Mater. Lett.* 163 (2016) 43-46.
- [10] Y. Suzuki, P. E. D. Morgan, T. Ohji, New uniformly porous CaZrO₃/MgO composites with three-dimensional network structure from natural dolomite, *J. Am. Ceram. Soc.* 83 (2000) 2091-2093.
- [11] Y. Suzuki and M. Morimoto, Uniformly porous MgTi₂O₅ with narrow pore-size distribution: *in situ* processing, microstructure and thermal expansion behavior, *J. Ceram. Soc. Jpn.* 118 (2010) 1212-1216.
- [12] Y. Suzuki, T. S. Suzuki, Y. Shinoda, and K. Yoshida, Uniformly porous MgTi₂O₅ with narrow pore-size distribution: XAFS study, improved in-situ synthesis, and new *in-situ* surface coating, *Adv. Eng. Mater.* 14 (2012) 1134-1138.
- [13] B. Schmid, N. Aas, O. Grong, R. Odegard, High-temperature oxidation of nickel and chromium studied with an in-situ environmental scanning electron microscope, *Scanning* 23 (2001) 255-266.

- 1
2
3 [14] G.G.E. Seward, D.J. Prior, J. Wheeler, S. Celotto, D.J.M. Halliday, R.S. Paden, M.R. Tye,
4 High-temperature electron backscatter diffraction and scanning electron microscopy imaging
5 techniques: in-situ investigations of dynamic processes, *Scanning* 24 (2002) 232-240.
6
7 [15] A.J. Smith, H.V. Atkinson, S.V. Hainsworth, A.C.F. Cocks, Use of a micromanipulator at high
8 temperature in an environmental scanning electron microscope to apply force during the
9 sintering of copper particles, *Scripta Mater.* 55 (2006) 707-710.
10
11 [16] M.L. No, A. Ibarra, A. Lopez-Echarri, E.H. Bocanegra, J. San Juan, Diffusion processes in
12 Cu-Al-Ni shape memory alloys studied by mechanical spectroscopy and in situ transmission
13 electron microscopy at high temperatures, *Mater. Sci. Eng. A* 442 (2006) 418-422.
14
15 [17] H. Kruger, V. Kahlenberg, V. Petricek, F. Phillipp, W. Wertl, High-temperature structural
16 phase transition in $\text{Ca}_2\text{Fe}_2\text{O}_5$ studied by in-situ X-ray diffraction and transmission electron
17 microscopy, *J. Solid State Chem.*, 182 (2009) 1515-1523.
18
19 [18] J. Bezjak, A. Recnik, B. Jancar, P. Boullay, I.R. Evans, D. Suvorov, High-temperature
20 transmission electron microscopy and X-ray powder diffraction studies of polymorphic phase
21 transitions in $\text{Ba}_4\text{Nb}_2\text{O}_9$, *J. Am. Ceram. Soc.* 92 (2009) 1806-1812.
22
23 [19] D. Varandani, K. Agarwal, J. Brugger, B.R. Mehta, Scanning thermal probe microscope
24 method for the determination of thermal diffusivity of nanocomposite thin films, *Rev. Sci.*
25 *Instrum.* 87 (2016) 084903.
26
27 [20] M. Reid, D. Phelan, R. Dippenaar, Concentric solidification for high temperature laser
28 scanning confocal microscopy, *ISIJ Int.* 44 (2004) 565-572.
29
30 [21] S.S. Jung, I. Sohn, Effect of FeO Concentration on the crystallization of high-temperature
31 $\text{CaO-Al}_2\text{O}_3\text{-MgO-FeO}$ Melts, *J. Am. Ceram. Soc.* 96 (2013) 1309-1316.
32
33 [22] P. Yan, Y.J. Jeong, M. F. Islam, P. C. Pistorius, Real time and in situ observation of graphene
34 growth on liquid metal surfaces via a carbon segregation method using high-temperature
35 confocal laser scanning microscopy, *RSC Adv.* 6 (2016) 101235-101241.
36
37 [23] I. Sohn, R. Dippenaar, In-situ observation of crystallization and growth in high-temperature
38 melts using the confocal laser microscope, *Metal. Mater. Trans. B* 47 (2016) 2083-2094.
39
40 [24] Y. Nakagoshi and Y. Suzuki, Dimensional change behavior of porous MgTi_2O_5 in reactive
41 sintering, *Ceram. Int.*, in press <http://dx.doi.org/10.1016/j.ceramint.2017.01.079>
42
43 [25] G. Bayer, Thermal Expansion Characteristics and stability of pseudobrookite-type compounds,
44 Me_3O_5 , *J. Less Common Met.* 24 (1971) 129-138.
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

1
2
3 **Figure Captions**
4

5 **Fig. 1** SEM images of (a) the $\text{Mg}_5(\text{CO}_3)_4(\text{OH})_2 \cdot 4\text{H}_2\text{O} - \alpha\text{-Fe}_2\text{O}_3 - \text{Nb}_2\text{O}_5$ mixed powder and (b) its
6 heat-treated-only product (SPGs) at 1350°C; (c) digital optical microscope image of SPGs.
7
8 Reproduced with permission from [9] with the license No. 4032800187654. Copyright
9 2016 Elsevier.
10

11
12 **Fig. 2** Multiple screens for the classification of spherical porous granules.
13

14
15 **Fig. 3** Microstructure development of spherical porous granules (SPGs) observed by *in situ*
16 high-temperature confocal laser-scanning microscopy (HT-CLSM). Percentages in photos
17 show the diameter change of a selected granule during the heating.
18
19
20
21

22
23 **Fig. 4** XRD pattern of spherical porous granules, showing almost single-phase MgFeNbO_5 with
24 trace spinel phase.
25
26

27
28 **Fig. 5** SEM-EDS wide-area analysis of a MgFeNbO_5 SPG, showing 11.6 at.% Mg, 11.9 at.% Fe,
29 12.1 at.% Nb and 64.5 at.% O, which are close to the ideal composition of MgFeNbO_5 :
30 12.5 at % of each metal and 62.5 at % of oxygen.
31
32

33
34 **Fig. 6** SEM micrographs, particle-size distributions and aspect ratio for spherical porous
35 granules (SPGs) after multiscreen classification: (a) sampling from the screens between
36 100 and 150 μm openings, and (b) sampling from the screens between 75 and 100 μm
37 openings.
38
39

40 **Fig. 7** Schematic illustration of the microstructure development during the heating.
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

1
2
3 **Spherical porous granules in MgO–Fe₂O₃–Nb₂O₅ system: *In situ* observation of formation**
4 **behavior using high-temperature confocal laser-scanning microscopy**
5
6


7 Yoshikazu Suzuki,^{a*} Hiroya Abe^b, Hajime Yamamoto^b, Kazuhiro Ito^b, Hiroshige Inoue^b, Mayumi
8 Nakamura^c

9 ^a Faculty of Pure and Applied Sciences, University of Tsukuba, 1-1-1 Tennodai, Tsukuba, Ibaraki,
10 305-8573, Japan

11 ^b Joining and Welding Research Institute, Osaka University, 11-1 Mihogaoka, Ibaragi, Osaka
12 567-0047, Japan

13 ^c Yonekura MFG Co., 2-11-5, Shin-Yokohama, Kohoku, Yokohama, Kanagawa, 222-0033, Japan
14
15

16 **Supplement**
17
18
19

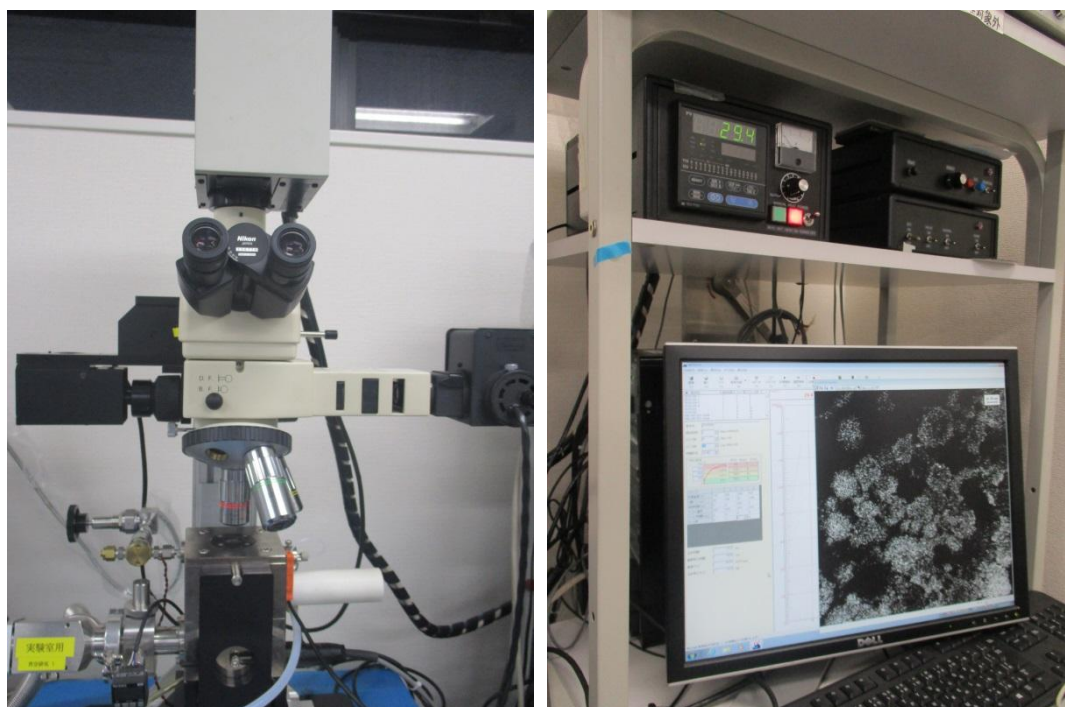

43
44
45 **Fig. S1** Appearance and controller of a high-temperature confocal laser-scanning microscope.
46
47
48
49
50
51
52
53
54
55
56

57

* Corresponding Author

58 E-mail: suzuki@ims.tsukuba.ac.jp

59 Tel: +81-29-853-5026 / Fax: +81-29-853-4490
60
61
62
63
64
65

Figure1
[Click here to download high resolution image](#)

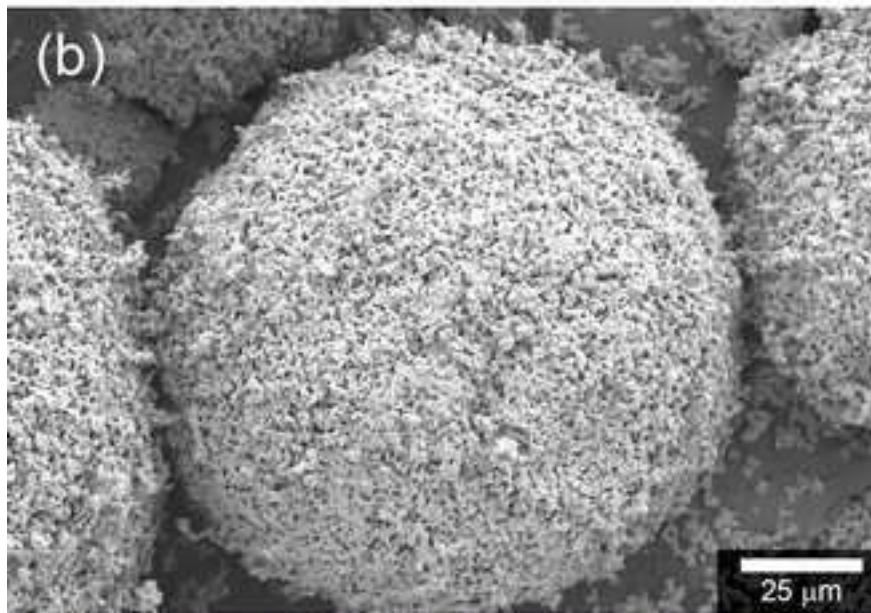
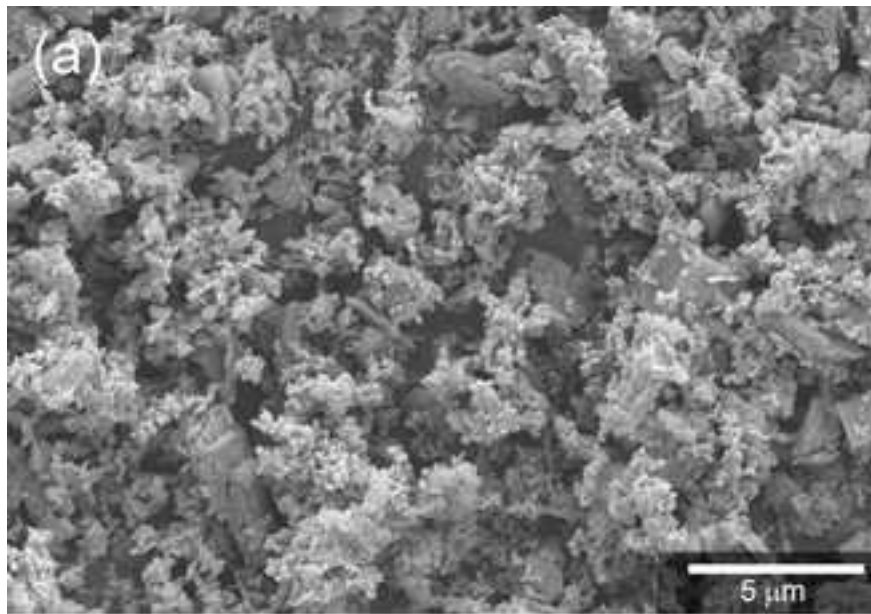


Figure2

[Click here to download high resolution image](#)

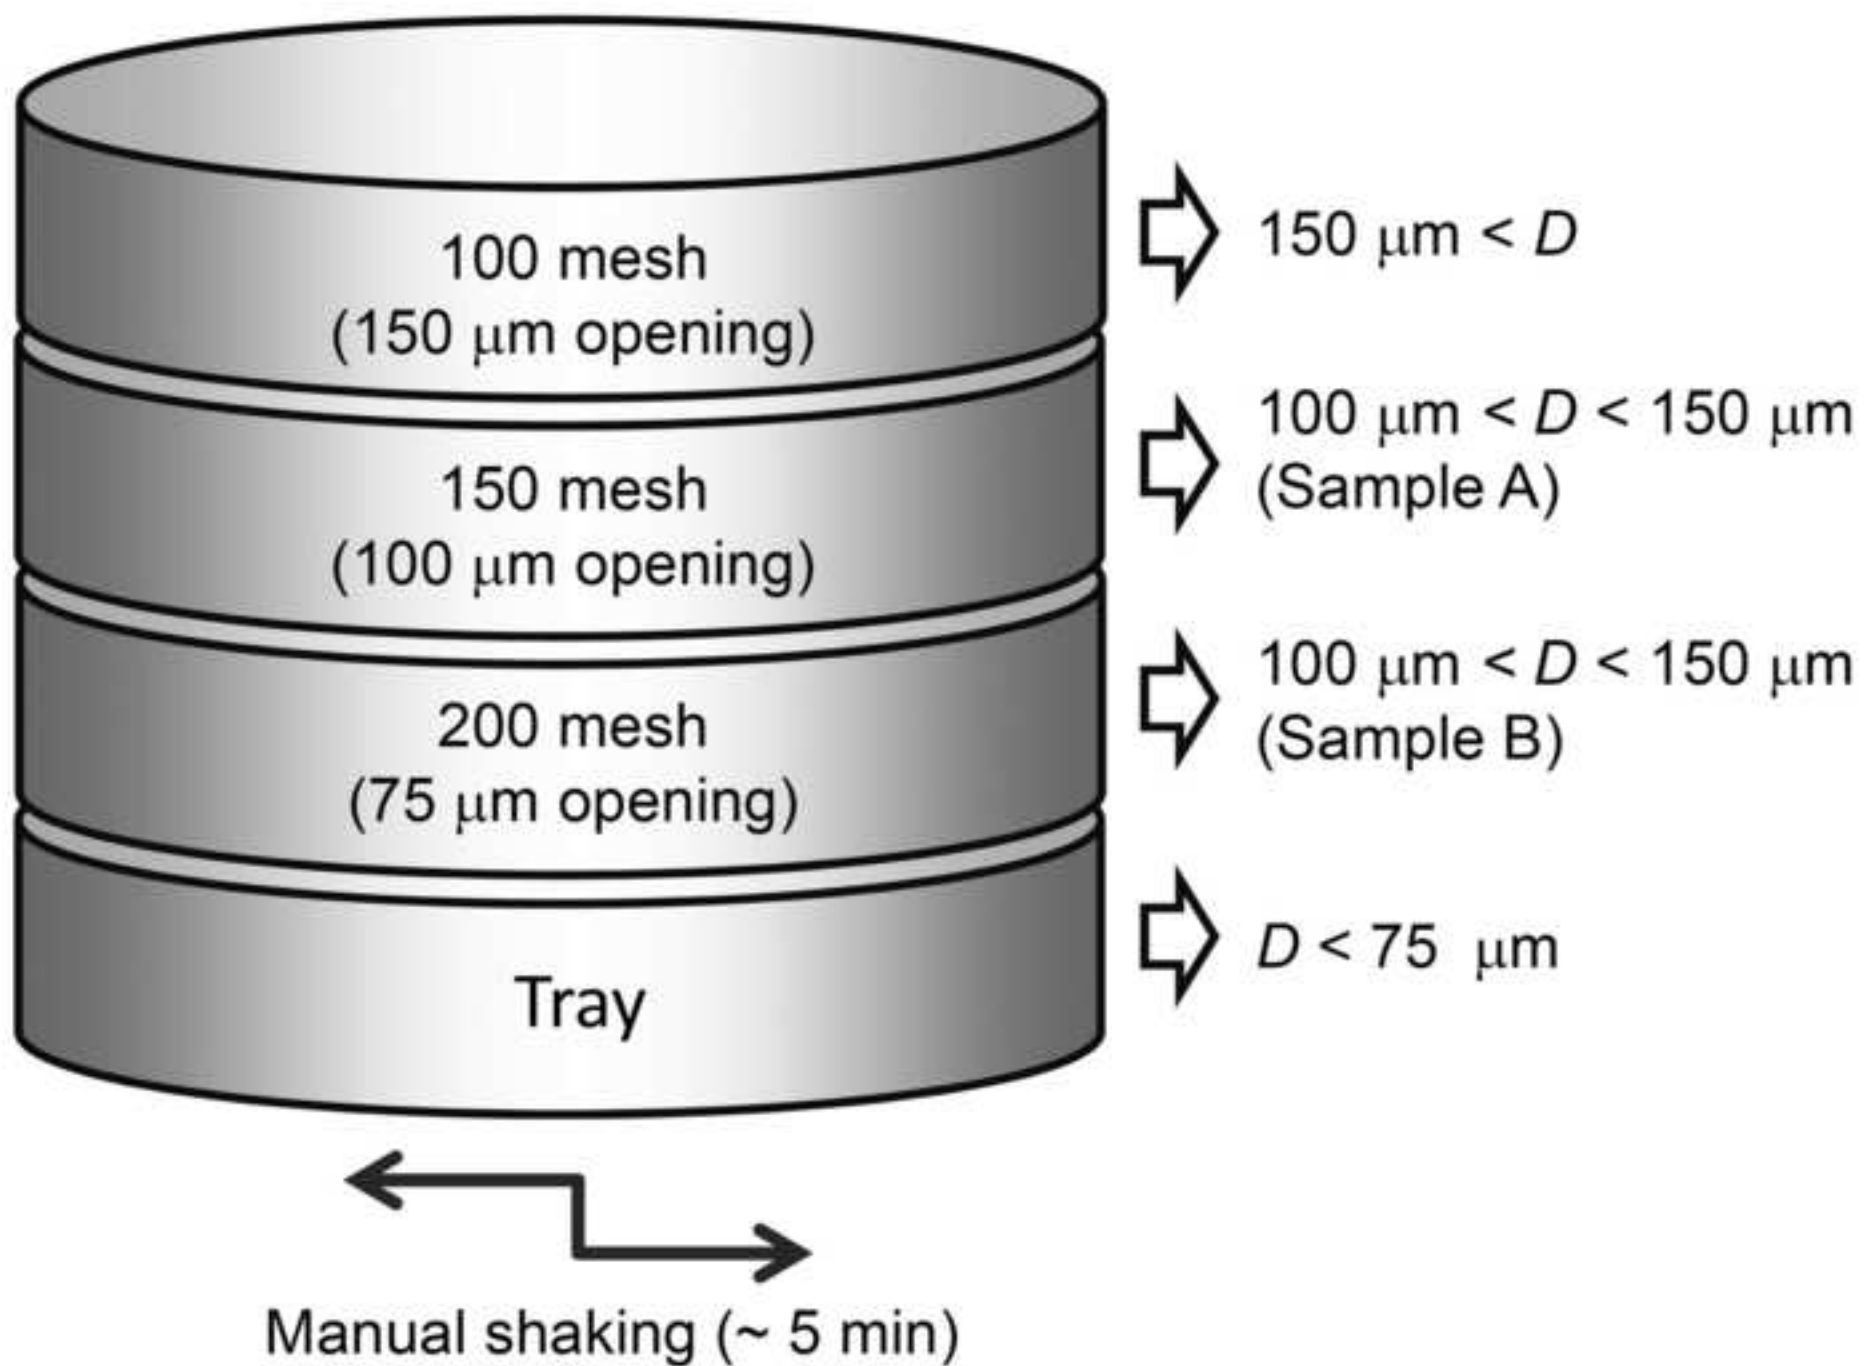


Figure3
[Click here to download high resolution image](#)

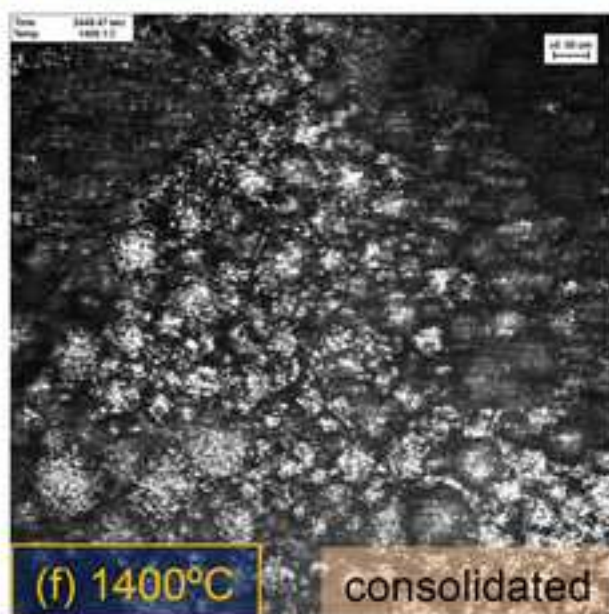
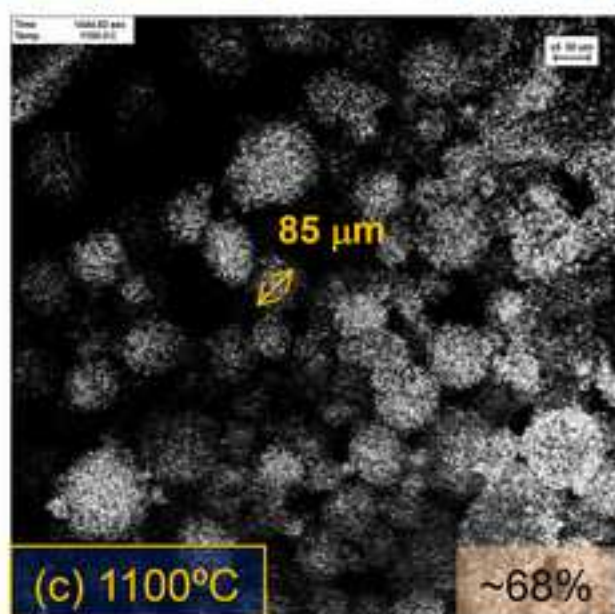
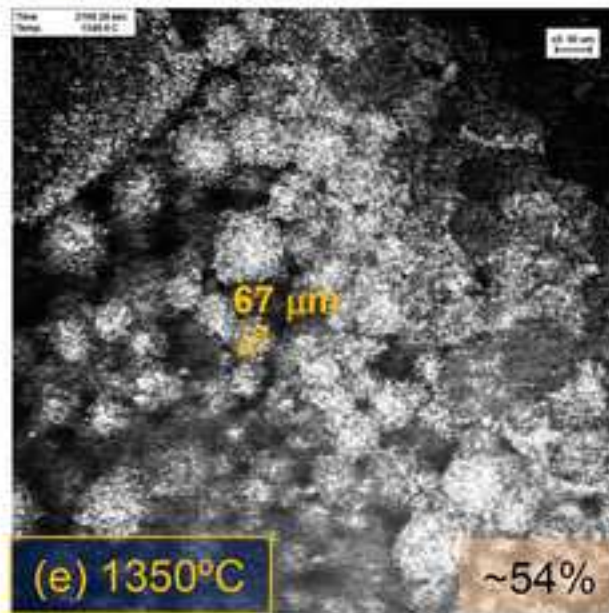
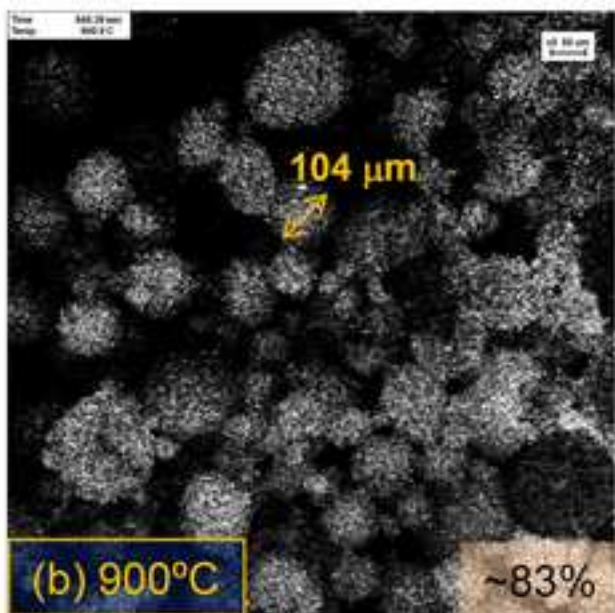
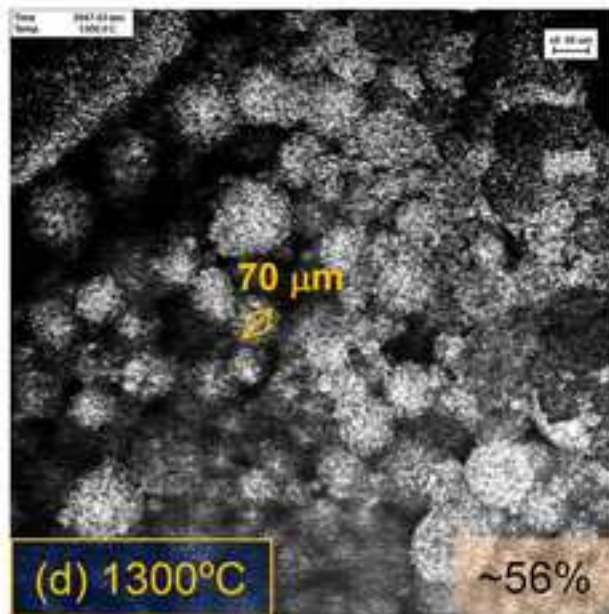
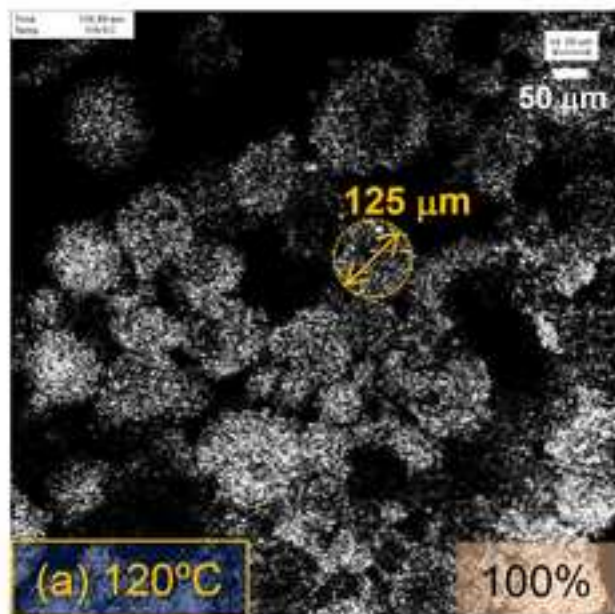


Figure4

[Click here to download high resolution image](#)


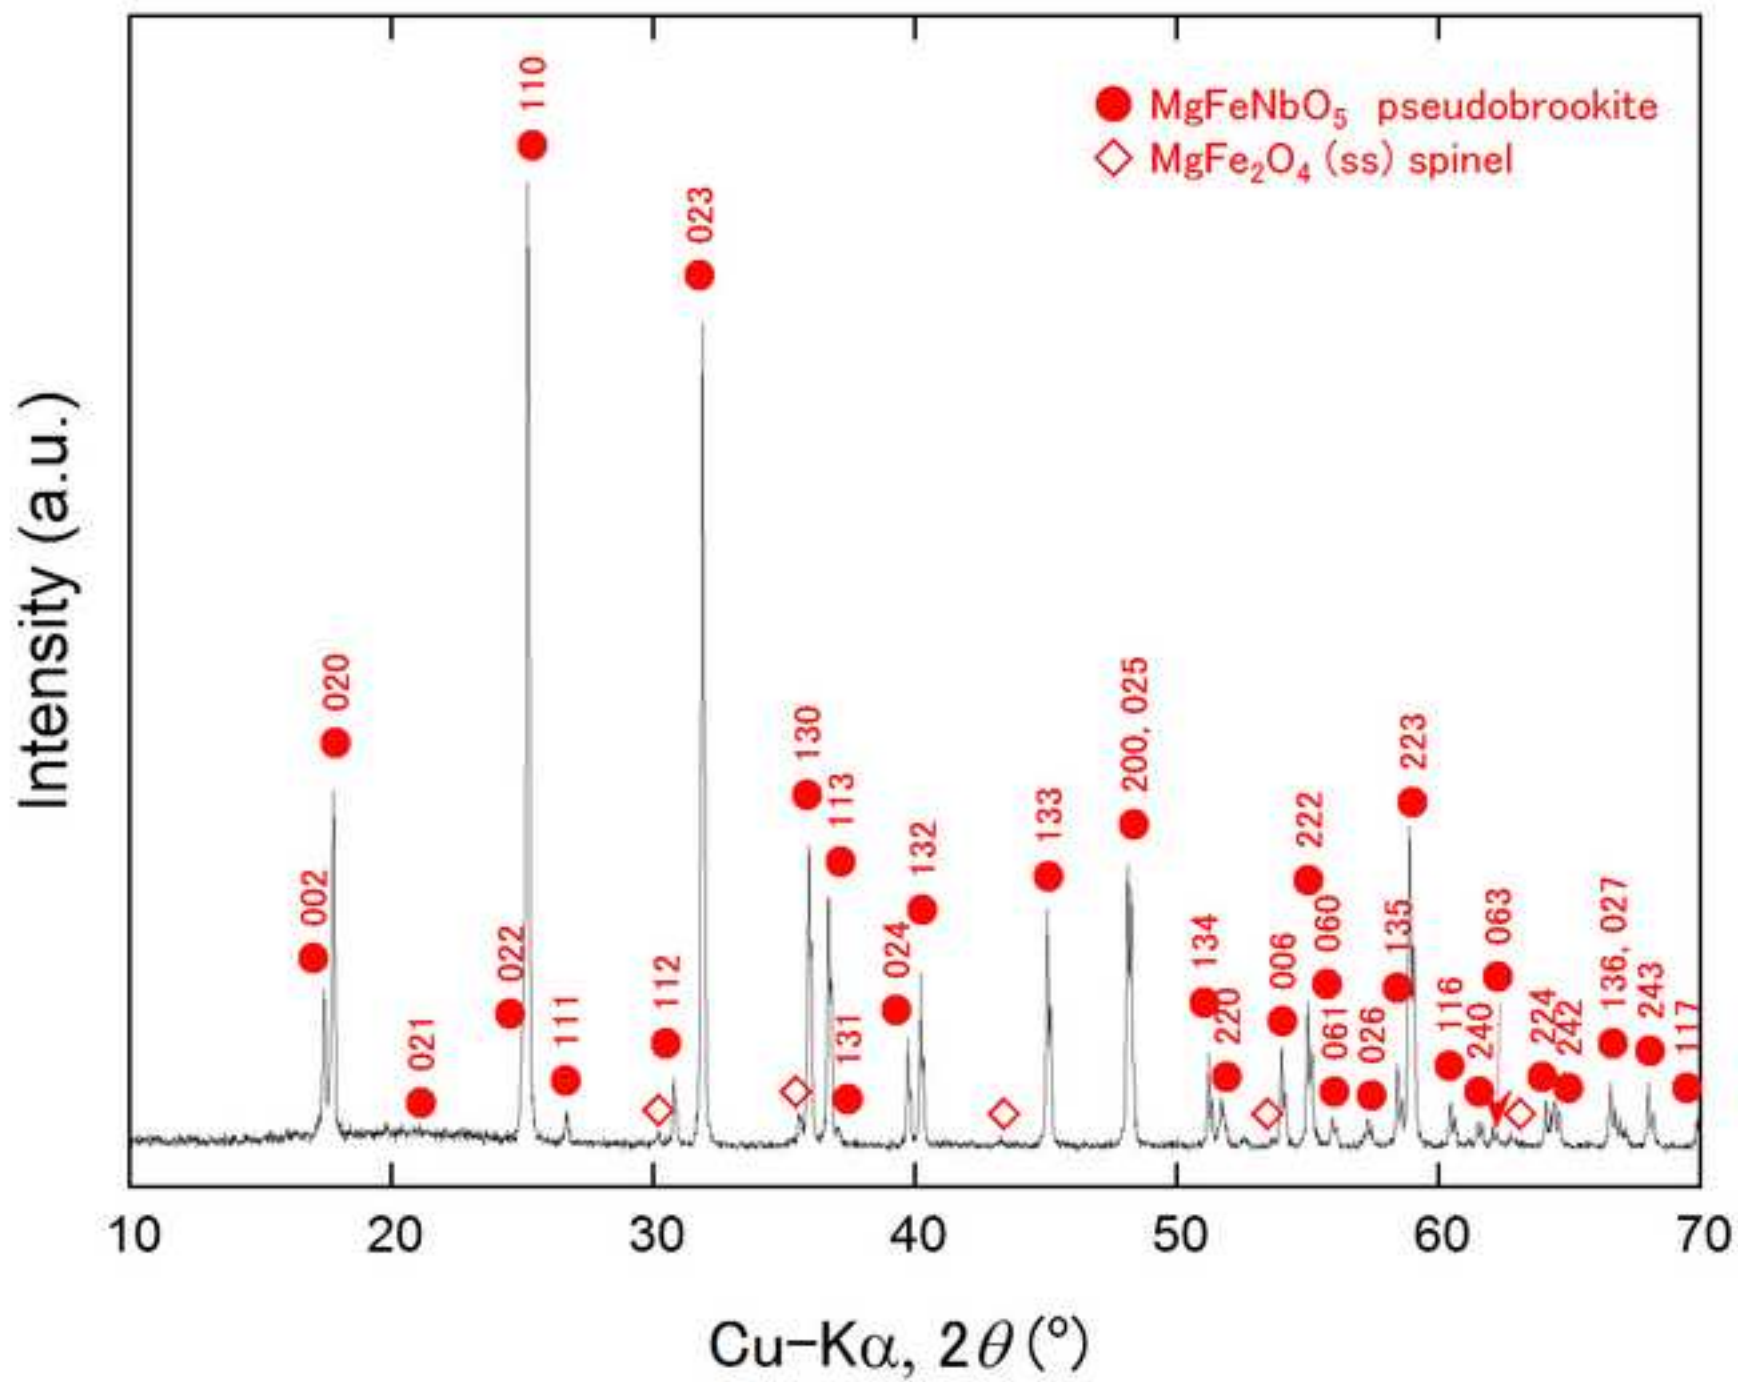


Figure5

[Click here to download high resolution image](#)

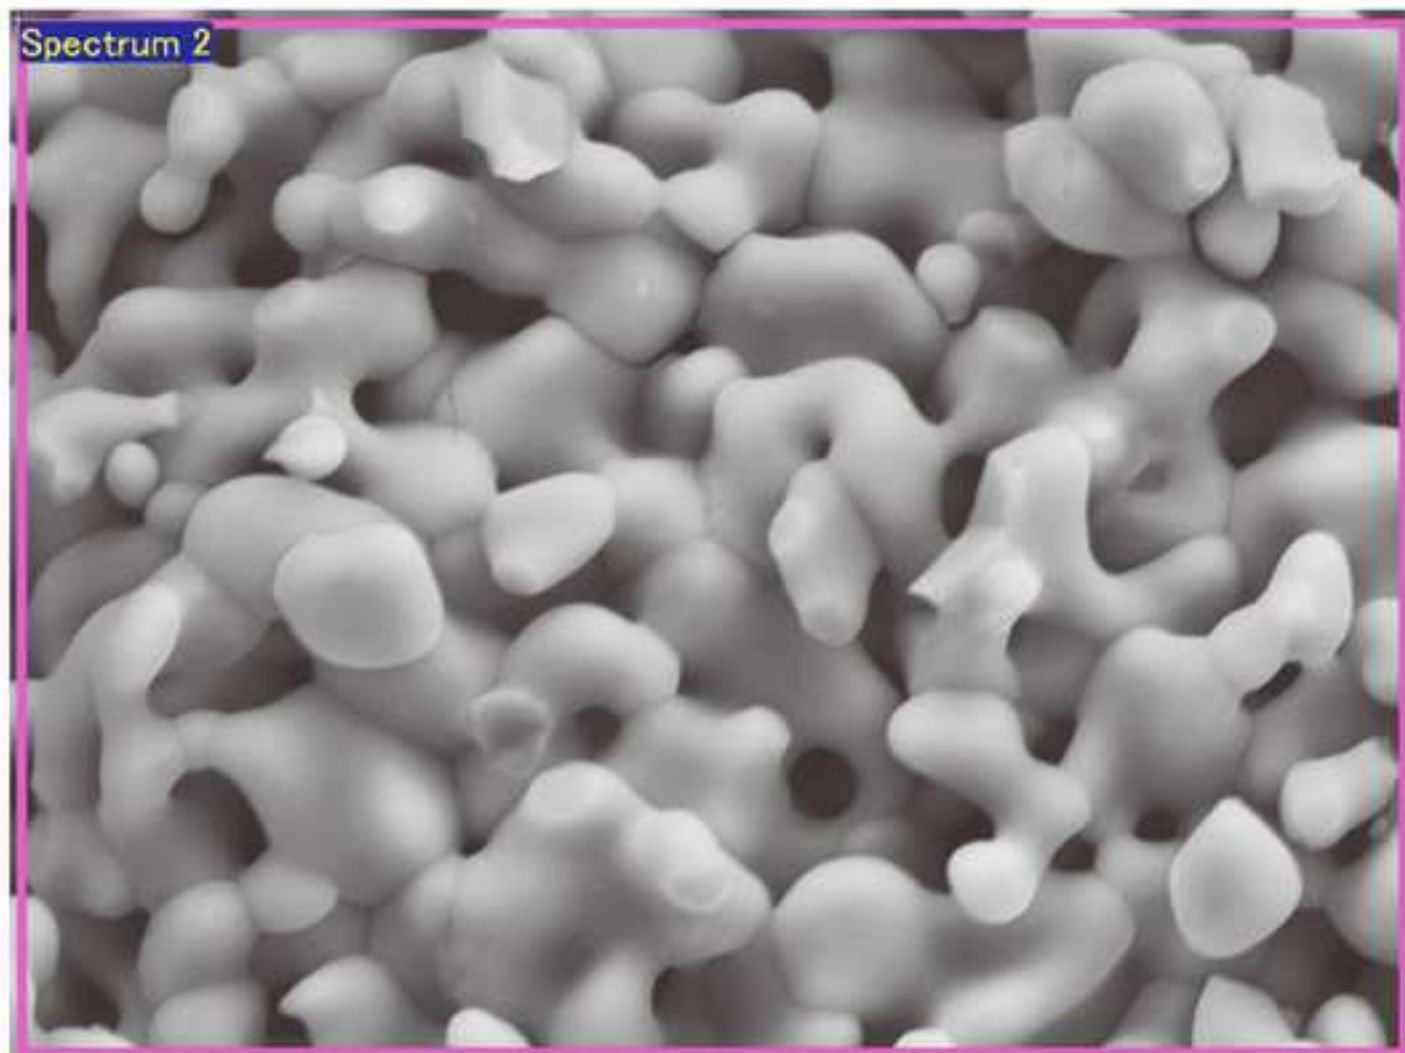

10 μm

Electron Image 1

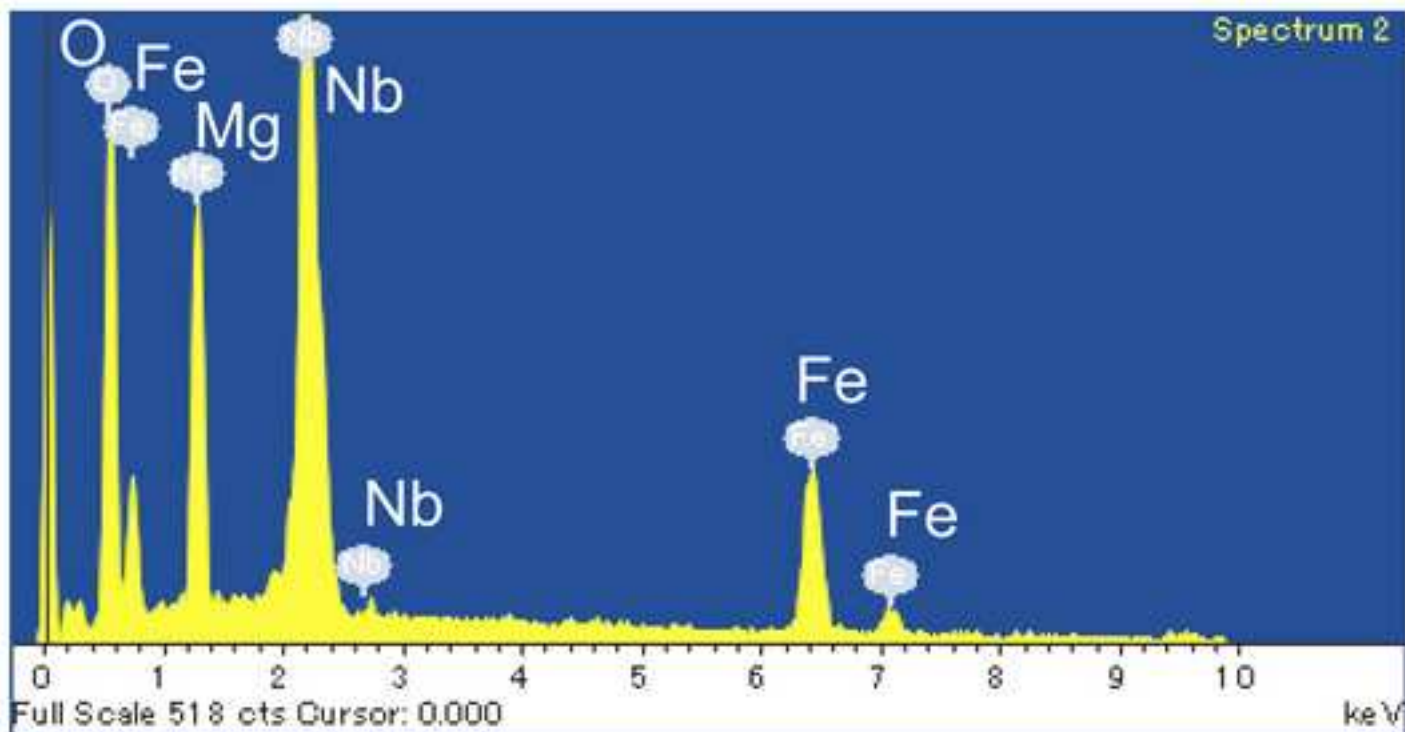


Figure6
[Click here to download high resolution image](#)






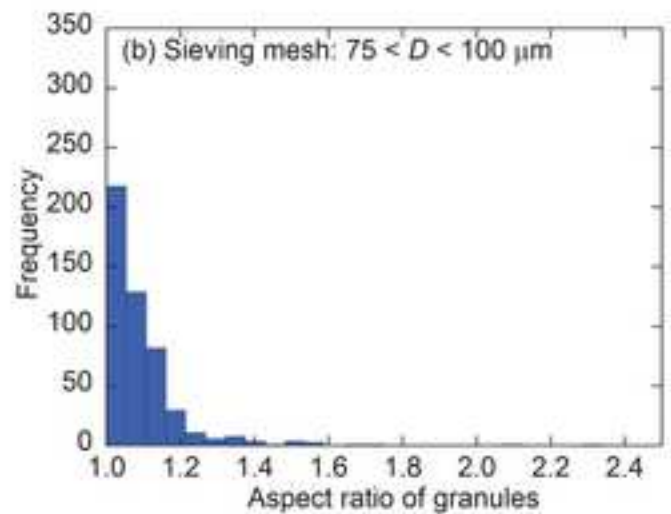


Figure7
[Click here to download high resolution image](#)

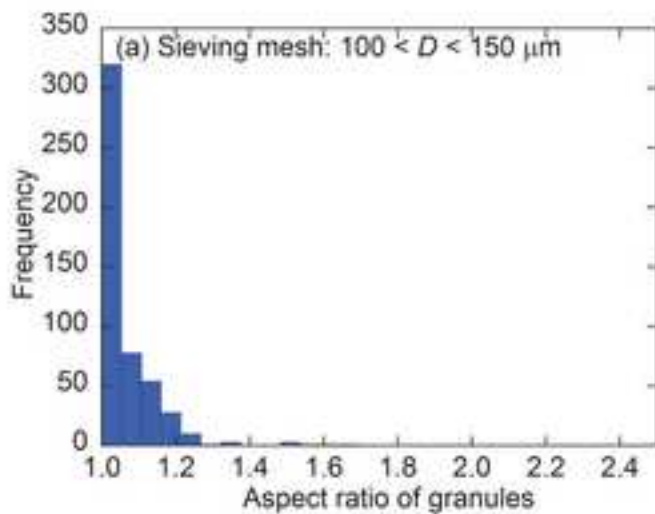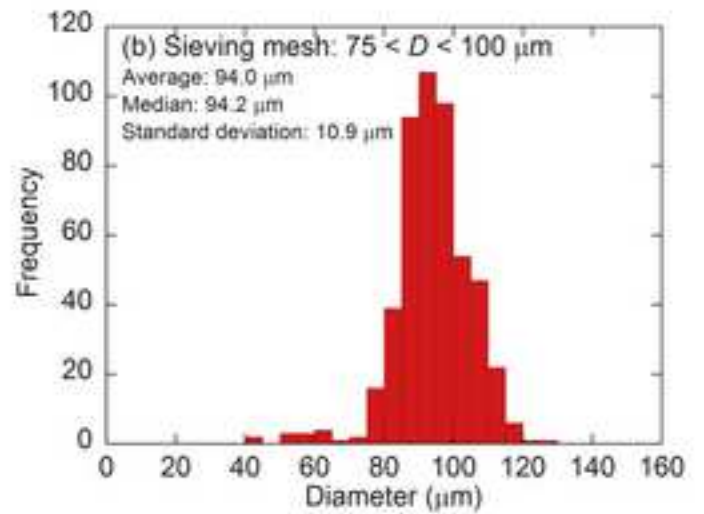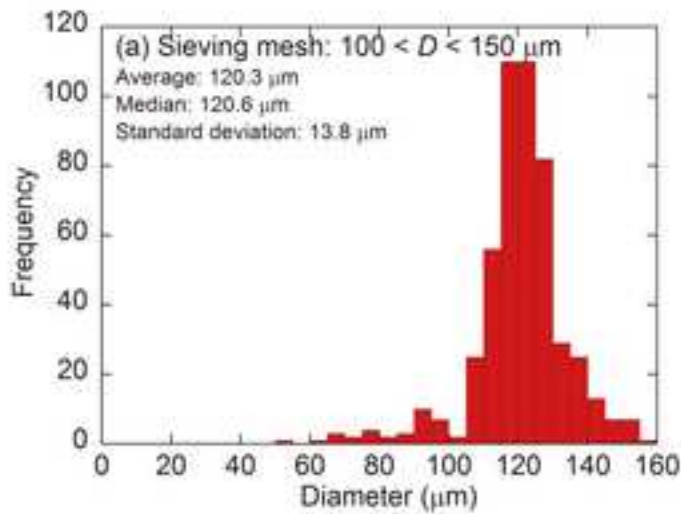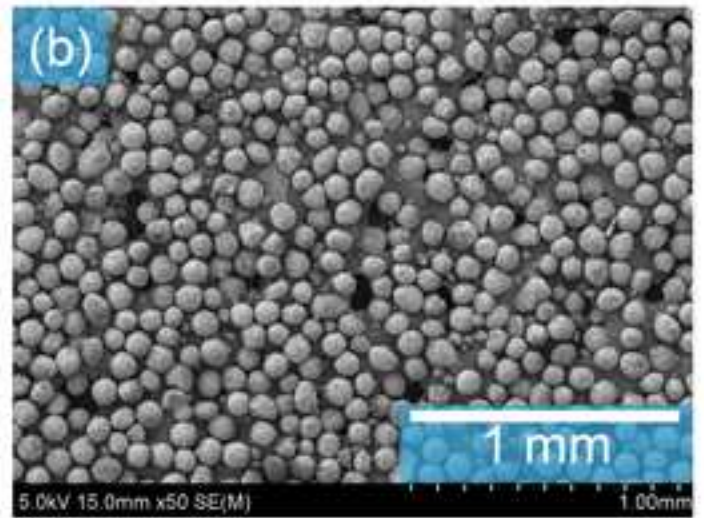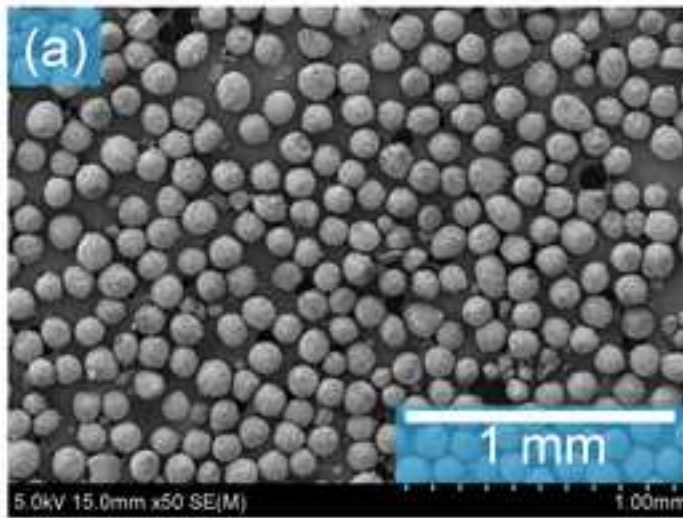